



REPORT DOCUMENTATION PAGE

1a. REPORT SECURITY CLASSIFICATION Unclassified		b. RESTRICTIVE MARKINGS	
2a. SECURITY CLASSIFICATION AUTHORITY		3. DISTRIBUTION AVAILABILITY OF REPORT This document has been approved for public release and sale; it's distribution is unlimited	
2b. DECLASSIFICATION/DOWNGRADING SCHEDULE			
4. PERFORMING ORGANIZATION REPORT NUMBER(S) Technical Report #5		5. MONITORING ORGANIZATION REPORT NUMBER(S) 4133046	
6a. NAME OF PERFORMING ORGANIZATION University of Minnesota	6b. OFFICE SYMBOL (If applicable) ONR	7a. NAME OF MONITORING ORGANIZATION Office of Naval Research	
6c. ADDRESS (City, State, and ZIP Code) Dept. of Chemical Eng. & Materials Science University of Minnesota Minneapolis, MN 55455		7b. ADDRESS (City, State, and ZIP Code) 800 Quincy Street North Arlington, VA 22217-5000	
8a. NAME OF FUNDING/SPONSORING ORGANIZATION Office of Naval Research	8b. OFFICE SYMBOL (If applicable) ONR	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER Grant NO0014-93-1-0563	
8c. ADDRESS (City, State, and ZIP Code) 800 North Quincy Street Arlington, VA 22217-5000		10. SOURCE OF FUNDING NUMBERS	
		PROGRAM ELEMENT NO.	PROJECT NO.
		TASK NO.	WORK UNIT ACCESSION NO.
11. TITLE (Include Security Classification) Atomic Force Microscopy of the Electrochemical Nucleation and Growth of Molecular Crystals			
12. PERSONAL AUTHOR(S) A. C. Hillier and M. D. Ward			
13a. TYPE OF REPORT Technical	13b. TIME COVERED FROM 5/1/93 TO 6/30/94	14. DATE OF REPORT (Year, Month, Day) 6/23/94	15. PAGE COUNT 1
16. SUPPLEMENTARY NOTATION			
17. COSATI CODES		18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)	
FIELD	GROUP	SUB-GROUP	
		Organic Conductors/Atomic Force Microscopy/Nucleation/ Fractals	
19. ABSTRACT (Continue on reverse if necessary and identify by block number) The atomic force microscope (AFM) was employed to examine the nanoscale morphology, surface topography, and growth and dissolution characteristics of single crystals of a series of organic charge transfer salts, specifically those comprising the tetracyanoquinodimethane (TCNQ) acceptor and tetrathiafulvalene (TTF), tetramethyltetraselenafulvalene (TMTSF), and bis-(ethylenedithiolo)tetrathiafulvalene (BEDT-TTF) donors. The dynamics of electrocrystallization were studied <u>in situ</u> on specific exposed crystal faces of these salts while the supersaturation was controlled by the applied electrochemical potential. Results indicate that the growth modes and the distribution and orientation of topographic features can be correlated with the strength and direction of solid state intermolecular bonding. In general, the nanoscale topographic structure resembled the macroscopic morphology, suggesting self-similarity across the length scales examined.			
DTIC QUALITY INSPECTED 2			
20. DISTRIBUTION AVAILABILITY OF ABSTRACT <input checked="" type="checkbox"/> UNCLASSIFIED UNLIMITED <input type="checkbox"/> SAME AS RPT <input type="checkbox"/> DTIC USERS		21. ABSTRACT SECURITY CLASSIFICATION Unclassified	
22a. NAME OF RESPONSIBLE INDIVIDUAL Robert Nowak		22b. TELEPHONE (Include Area Code) X832X 703-696-4409	22c. OFFICE SYMBOL ONR Code 1113

94-20301



94 7 1 055

Atomic Force Microscopy of the Electrochemical Nucleation and Growth of Molecular Crystals

Andrew C. Hillier and Michael D. Ward

Department of Chemical Engineering and Materials Science

University of Minnesota, 421 Washington Ave. SE, Minneapolis, MN 55455

Introduction

Molecular crystals containing organic components exhibit a variety of interesting and potentially useful electronic properties, including electrical conductivity, superconductivity, non-linear optical behavior, and ferromagnetism,¹ and also comprise the majority of pharmaceutical reagents.² Much of the interest in these materials stems from the ability to employ molecular-level "crystal engineering" strategies³ to control solid state intermolecular interactions in order to rationally manipulate crystal packing and, consequently, influence bulk physical and electronic properties. While these strategies have been employed in the design and synthesis of many organic crystals, the self-assembly, nucleation, and crystallization processes that are responsible for their formation are not well understood, particularly at the molecular and nanoscale level. This understanding is crucial if important crystal characteristics such as polymorphism, habit, morphology, inclusion formation, and defect density are to be controlled.

Recent developments in atomic force microscopy (AFM),⁴ however, now provide for *in situ* visualization of the early stages of growth of organic crystals in liquids, as evidenced by recent reports for these and other materials.^{5,6} This capability provides for dynamic observation of nucleation events, and the determination, at small length scales, of the distribution of topographic features (i.e. terraces, ledges and kinks) that play an important role in crystal growth.⁷ We herein report *in situ* AFM observations of the nanoscale morphology, surface topography, and growth and dissolution characteristics of single crystals of a series of organic charge transfer salts, specifically those comprising the tetracyanoquinodimethane (TCNQ) acceptor and tetrathiafulvalene (TTF), tetramethyltetraselenafulvalene (TMTSF), and bis-(ethylenedithio)tetrathiafulvalene (BEDT-TTF) donors with a variety of counter-ions.

Experimental

Atomic force microscopy (AFM) experiments were performed with a Digital Instruments Nanoscope III scanning probe microscope. *In situ* studies were accomplished with an AFM electrochemical fluid cell (Digital Instruments) in a three-electrode configuration. The working electrode consisted of either graphite or a mature single crystal surface while platinum and silver wires served as counter and quasi-reference electrodes, respectively. The counter and reference electrodes were placed in the outlet port of the fluid cell. Experiments were then performed in organic solutions of ethanol, propylene carbonate, or acetonitrile containing millimolar concentrations of the donor/acceptor and high concentrations of the counterion in a tetrabutylammonium salt, which also served as the supporting electrolyte.

Results and Discussion

A variety of conductive and insulating salts were examined with a range of bonding properties. The low-dimensional conductors typically exhibited one dominant bonding interaction. A strong preference for [100] ledges on the (001) face of the low-dimensional organic superconductor (TMTSF)₂ClO₄ is a consequence of strong intermolecular charge transfer interactions between TMTSF molecules stacked along this direction (Figure 1). The (001) face of (TMTSF)₂ClO₄ exhibits layer-by-layer growth and etching, in which the layers correspond to single unit cell heights of 13.3 Å. A terrace-ledge-kink mechanism⁸ is observed, with the direction of fastest growth and etching oriented along the TMTSF stacking axis.

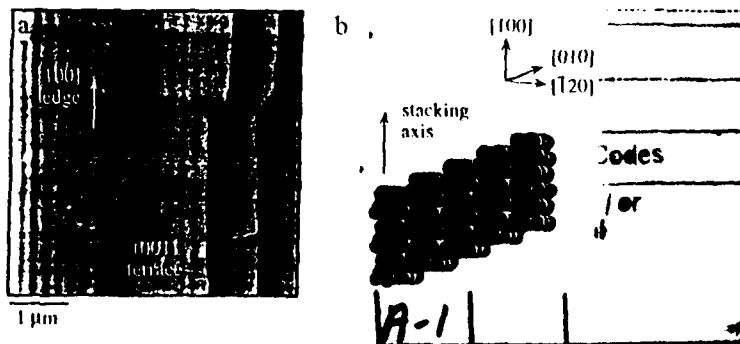


Figure 1: Molecular packing of the (001) plane of (TMTSF)₂ClO₄ and an AFM image of this face on a mature crystal showing (001) terraces bounded by [100] ledges. The [100] direction corresponds to the crystal stacking axis and is the direction of strongest intermolecular solid state bonding

Crystals of the low dimensional organic conductor (TTF)Bz₂ have also been imaged *in situ* following nucleation on a highly oriented pyrolytic graphite (HOPG) surface. These crystals exhibit a habit similar to that of the mature crystal and can be indexed using "AFM goniometry." The exposed crystal faces consist of low energy planes, as derived from the crystal structure, while the microscopic surface structure reflects solid state bonding. The observed growth mode varies with the particular crystal face examined. However, the [001] charge transfer axis manifests in the form of oriented topographical structures, namely dominant [001] ledges.

Several two dimensional salts were examined. The insulating salt, (Cp*Ru)₂(Cyclophane) (TCNQ)₂, exhibits two dominant bonding interactions, one electrostatic and the other van der Waals in nature, while a significant charge transfer interaction is absent. The resulting growth mode is clearly more two dimensional and exhibits a layer by layer evolution in the [110] direction. However, the presence of anisotropic electrostatic and van der Waals interactions in the plane of this face contributes to the formation of dominant ledge and kink structures (Figure 2). These ledges orient in the [110] and [111] directions. The two dimensional organic conductor α (BEDT-TTF)₂I₃ exhibits a similar layered growth mode with two dominant ledge directions.

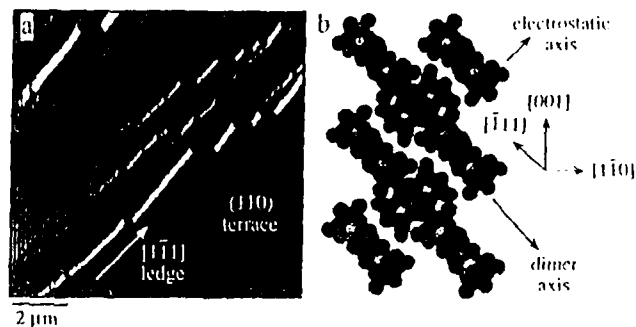


Figure 2: Layered growth of the (110) face of (Cp*Ru)₂(Cyclophane) (TCNQ)₂ that results from the two dominant bonding directions. (a) molecular packing of (011) face and (b) AFM image of growth. The [111] ledges are moving in the [111] direction

Conclusions

These studies illustrate that anisotropic solid state intermolecular forces play a dominant role in defining the nanoscale topography, etching and growth characteristics of molecular single crystal faces. In several examples described here, the behavior is dominated by nanoscale ledge structure that is coincident with directions of strong intermolecular electrostatic and charge transfer interactions. The role of excess interfacial energy during crystal growth is evident from the distribution of terraces, ledges, and kinks that differs from that observed under equilibrium conditions. These observations indicate that the surface topography is related to the morphology of macroscopic crystals, suggesting self-similarity of morphology during the crystal growth process.

Acknowledgements

The authors would like to acknowledge the support of the Office of Naval Research and the Center for Interfacial Engineering (NSF Engineering Research Centers Program). ACH would like to acknowledge the Upjohn Company for support in the form of an Upjohn Fellowship during 1992-93.

References

- 1 J.S. Miller, *Extended Linear Chain Compounds* (Plenum, New York, 1982), v.1-3. (b) J. Zyss and G. Tsoucaris, *Structure and Properties of Molecular Crystals*, M. Pienrot, Ed. (Elsevier, Amsterdam, 1990), pp. 297-350.
- 2 S.R. Byrn, *Solid State Chemistry of Drugs*, (Acad. Press, New York, 1982).
- 3 (a) G. Schmidt, *Pure Appl. Chem.* **27**, 617, (1971). (b) G. Desiraju, *Crystal Engineering - The Design of Organic Solids* (Elsevier, New York, 1989).
- 4 G. Binnig, C.F. Quate, and Ch. Gerber, *Phys. Rev. Lett.* **12**, 930 (1986).
- 5 (a) A.J. Gratz, S. Manne, and P.K. Hansma, *Science*, **251**, 1343 (1991). (b) S.D. Dubin and W.E. Carlson, *J. Cryst. Growth*, **122**, 71 (1992).
- 6 B. Drake, C.R. Prater, A.L. Weisenborn, S.A.C. Gould, T.R. Albrecht, C.F. Quate, D.S. Cannell, G.H. Hansma and P.E. Hansma, *Science*, **243**, 1586 (1989).
- 7 P. W. Carter, A. C. Hillier and M. D. Ward, *J. Am. Chem. Soc.* in press.
- 8 Tiller, W. A. *The Science of Crystallization: Microscopic Interfacial Phenomena* Cambridge University Press, New York, 1991, pp. 327-381.